

湿法磷酸萃取技术发展现状与研究进展

黄欣雨¹⁾, 甘晨¹⁾, 张名扬¹⁾, 邱丽娜^{1,2)}✉, 弓爱君^{1,2)}, 董艺¹⁾

1) 北京科技大学化学与化学工程学院, 北京 100083 2) 北京科技大学功能分子与晶态材料科学与应用北京市重点实验室, 北京 100083

✉通信作者, 邱丽娜, E-mail: qiulina@ustb.edu.cn

摘要 磷酸作为一种重要的化工原料, 在化工业中占有极其重要的地位。磷酸的应用主要由磷酸的纯度决定。低纯度磷酸可用于工业和农业领域, 而高纯度磷酸则可用于医药、食品和电子等行业。我国磷矿石以低品位磷矿为主, 主要用湿法磷酸处理, 相比热法磷酸更加清洁环保, 但产品杂质含量多种类复杂, 故发展磷酸净化技术尤为重要。本文从湿法磷酸纯化技术中的萃取法出发, 综述了萃取法的主要研究进展。重点介绍了溶剂萃取法、双水相萃取法、反胶团萃取法、超声协助萃取法和超临界流体萃取法的基本原理和发展趋势。分析了不同萃取方法的优缺点、分离效果和适用条件。突出介绍了溶剂萃取法, 梳理了磷酸除杂的主要萃取剂, 特别强调了复合萃取剂和新型萃取剂在磷酸纯化方面的显著优势, 最后, 对磷酸的萃取技术做出了前景展望。

关键词 磷酸; 湿法磷酸; 萃取; 萃取剂; 双水相萃取; 反胶团萃取; 超声协助萃取; 超临界流体萃取

分类号 TF791

Development status and research progress of wet phosphoric acid extraction technology

HUANG Xin-yu¹⁾, GAN Chen¹⁾, ZHANG Ming-yang¹⁾, QIU Li-na^{1,2)}✉, GONG Ai-jun¹⁾, DONG Yi¹⁾

1) School of Chemistry and Biological Engineering, University of Science and Technology Beijing, Beijing100083, China

2) Beijing Key Laboratory for Science and Application of Functional Molecular and Crystalline Materials, University of Science and Technology Beijing, Beijing 100083, China

✉ Corresponding author, QIU Li-na, E-mail: qiulina@ustb.edu.cn

ABSTRACT As an important chemical raw material, phosphoric acid occupies an extremely important position in the chemical industry. The application of phosphoric acid is mainly determined by the purity of phosphoric acid, low purity phosphoric acid can be used in industrial and agricultural neighborhoods, while high purity phosphoric acid can be used in pharmaceutical, food, electronics and other industries. In recent years, with the increasing demand for batteries and semiconductors, the purity of phosphoric acid has put forward higher requirements. There are two main manufacturing methods of phosphoric acid, among them, thermal phosphoric acid consumes large energy and environmentally unfriendly, which does not meet the needs of China's development of green chemistry. Wet phosphoric acid has low energy consumption and bulk and complex product impurities, which is more suitable for treating low-grade phosphate rock in China. Compared with chemical precipitation, crystallization, electrodialysis, ion exchange resin and other purification technologies, the extraction method has the advantages of green environment, simple operation and large production capacity, and is a phosphoric acid purification method with great development prospects. This article summarizes in detail the research status of various extraction methods in recent

基金项目: 国家重点研发计划项目 (2017YFF0106006); 校企合作开发项目 (2023-0789); 2023 年本科生

科技创新创业训练项目。

years. The basic principles and development trends of solvent extraction, aqueous two-phase extraction, reverse micelles extraction, ultrasonic-assisted extraction and supercritical fluid extraction were emphatically introduced, and the solvent extraction method and various extractants were emphatically sorted out. The research of single extractants such as tri-n-butyl phosphate (TBP), methyl isobutyl ketone (MIBK), and n-octanol (NOA) mainly focuses on exploring the optimal extraction conditions (O/A phase ratio, temperature, and air pressure), but a single extractant can usually only extract a single impurity and cannot meet the extraction of multiple impurities, so the composite extractant has significant advantages in phosphoric acid purification. At present, researches highlight composite extractants are mainly on the proportion of extractants (usually the volume ratio) and the optimal conditions for extraction. In addition to composite extractants, the new extractants can also solve the problem of low extraction efficiency of a single extractant. Finally, the future development trend of extraction technology of phosphoric acid is proposed: 1) development of green composite extractants, new extractants, new materials combined with extractants that can achieve efficient separation of impurities from phosphoric acid, 2) increase the research on the application of aqueous two-phase extraction and reverse micelles extraction in ion extraction, and explore new aqueous phase systems, 3) use ultrasonic technology to accelerate the extraction process, and study how supercritical fluids can improve the solubility and extraction efficiency of ions. Reduce costs and explore specific application areas.

KEY WORDS phosphoric acid; wet phosphoric acid; extraction; extractant; aqueous two-phase extraction; reverse micelles extraction; ultrasonic assisted extraction; supercritical fluid extraction

磷矿是国家的重要战略资源，在医药、军工、农业生产等诸多国家重点领域上都有着广泛的应用。以磷矿为原料制得的磷酸在国民经济中也有着重要地位。磷酸不仅是生产磷肥和磷酸盐的中间原料，还被广泛应用于烘焙、饮料、洗涤剂和食品添加剂等工业和家用领域。随着中国新能源和电子产业的发展，磷酸作为生产新型磷材料的基础资源，需求不断增加，具有广阔的应用前景。因此，开发现有磷矿生产磷酸已成为我国的当务之急。

工业上生产磷酸的方法主要有湿法和热法两种，所得产品分别称为湿法磷酸和热法磷酸。热法以黄磷为原料，在过量空气中燃烧水合后，得到纯度较高、杂质少的磷酸，提纯后可得到食品级磷酸。但因能耗大，生产成本高昂，工业上很少采用此法。湿法生产磷酸的主要原理是利用无机酸溶解矿石，浸出溶液得到磷酸。此法适用于低品位磷矿，能耗小，污染少，成本低，但得到酸纯度低，需要进一步纯化才能投入使用。据国家资源局统计，中国磷矿以中低品位磷矿为主，矿石 P_2O_5 平均品位仅为 16.85%，适合使用湿法处理磷矿。湿法磷酸目前占全球磷酸总产量的 85%-90%^[1]，但这种方法制得的产品存在各种悬浮的、溶解的杂质和重金属离子。因此，湿法磷酸或来自湿法工艺的磷酸盐通常仅用于生产对磷酸纯度要求低的磷肥，不能用于新能源和电子等对磷酸纯度要求极高的行业。想要获取高纯度的磷酸，就必须扩大磷酸纯化的研究工作。

目前湿法磷酸净化的方法有：物理吸附法、化学沉淀法、溶剂萃取法、离子交换法、结晶法等。其中，萃取法中的溶剂萃取是目前湿法磷酸净化所使用的最广泛的方法^[2]，而溶剂萃取中萃取剂的选择是该方法的关键所在^[3]。因此，本文综述了醇类、酯类、酮类等不同种类的萃取剂和复合萃取剂对湿法磷酸的净化效果。同时还将溶剂萃取法与双水相萃取法、反胶团萃取法、超声协助萃取法和超临界流体萃取法进行对比研究。

1 湿法磷酸中的杂质种类

湿法磷酸中的杂质大多数来自原料磷矿（Phosphate rock, PR）^[4]和硫酸药剂，少量来自生产过程中添加的药剂，以及设备与管道的磨蚀和腐蚀^[5]。不同来源的磷矿中主要元素

的含量如表 1。湿法磷酸中的主要杂质如表 2。

表 1 不同来源磷矿中主要元素的含量^[4]

Table 1 The concentration of major elements in the phosphate rocks from various origins^[4]

Constituents	PR1	PR2	PR3	PR4	PR5
P ₂ O ₅	29.0	28.7	30.4	29.4	31.2
CaO	53.2	53.4	57.1	48.4	55.8
Al ₂ O ₃	0.51	0.33	0.13	0.44	0.51
F	3.12	3.53	3.32	3.47	4.07
Fe ₂ O ₃	0.64	0.21	0.27	0.55	2.31
K ₂ O	0.20	0.10	0.22	0.22	0.13
MgO	1.31	0.341	0.348	1.01	0.413
Na ₂ O	1.54	0.61	0.52	1.09	0.6
SO ₃	3.36	1.46	2.68	2.71	2.36
SiO ₂	2.93	8.67	1.67	2.66	5.77
SrO	0.27	0.19	0.25	0.26	0.12

表 2 湿法磷酸中的主要杂质^[5]

Table 2 Main impurities in wet process phosphoric acid^[5]

The main dissolved impurities in wet phosphoric acid		The main insoluble impurities in wet phosphoric acid	
Cationic type	Anionic type	Crystalline	Colloidal type
Ca ²⁺ , Mg ²⁺ , Pb ²⁺ , Fe ³⁺ , Al ³⁺ , As ³⁺ , K ⁺ , Na ⁺ , Fe ²⁺ , etc.	Cl ⁻ , SO ₄ ²⁻ , F ⁻ , etc.	Undecomposed phosphate and gangue ores, sulfates, fluorides, fluorosilicates, etc.	SiO ₂ ·nH ₂ O, acidic phosphate of iron, aluminum and potassium, acidic phosphate of iron and sodium, etc.

2 萃取法

2.1 溶剂萃取

溶剂萃取法是去除湿法磷酸中杂质最有效的方法^[6]，也被称为溶质的两相分布，其定义为溶质在两个相互接触的不混相液相中的分散^[7]，如图 1 所示。工艺流程主要由萃取、洗涤、反萃取三个基本步骤构成，在磷酸中加入非互溶性或低互溶性的有机萃取剂进行萃取，之后再行洗涤操作，此时已经脱除磷酸中的大部分阳离子和阴离子杂质，最后用纯净水反萃得到净化后的磷酸。

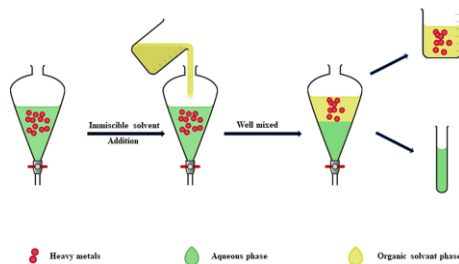


图 1 溶剂萃取原理^[8]

Fig.1 Solvent extraction principle^[8]

2.1.1 常见萃取剂

醇类萃取剂是目前各大研究机构使用最多的溶剂^[9]，主要有正丁醇^[10]、正己醇^[10]、正辛醇（NOA）^[10-12]等。Amin 等^[10]采用丁醇、己醇、辛醇为萃取剂纯化磷酸商业磷酸。在 25 °C，9.2 M 商业磷酸，丁醇、己醇、辛醇的水/有机比 1:1、1:3、1:5 的条件下，丁醇、己醇和辛醇的萃取率分别为 86%、94%和 87%。酯类萃取剂有磷酸三丁酯（TBP）、丁基-N，N-二（2-乙基己基）氨基甲酰基壬基膦酸酯（DEHCNPB）^[13]等。为改善传统提取工艺在萃取效率、磷收率和余液利用率等方面不理想的问题，Wang 等^[14]报道了一种以 P507（乙基己基磷酸单-2-乙基己酯）为萃取剂，高效、深度去除粉煤灰硫酸浸出液中 Fe³⁺的可持续

方法。在最佳条件下, Fe^{3+} 的有效去除率可达 97.6% 以上。酮类萃取剂以甲基异丁基酮 (MIBK) 为主。Torabi 等^[15] 在不同温度 (298.2 K、308.2 K、318.2 K) 和相同气压 (101.3 KPa) 下探究 1-戊醇和 MIBK 的溶解度曲线, 研究结果表明, 随着温度的升高, 1-戊醇和 MIBK 的萃取效果逐渐降低; 甲基异丁基酮的萃取效果优于 1-戊醇, 可能是因为酮中的羰基官能团 (由于氢化性质) 比醇中的羟基官能团具有更好的分离因子。

其他萃取剂如二丁基亚砷 (BDSO)^[16] 在萃取过程中可形成萃取物 $\text{H}_3\text{PO}_4 \cdot 0.3\text{BDSO}$, 对 Mg^{2+} 和 Al^{3+} 的选择性较强, 对 Fe^{3+} 、 F^- 和 SO_4^{2-} 的选择性适中, 可用于低品位磷矿湿法磷酸的萃取。Cao^[17, 18] 等分别研究了四元体系硝酸+硝酸钙+水+三辛胺 (TOA) 和五元体系硝酸+磷酸+硝酸钙+水+TOA 的萃取效率。得出结论, 相比于硝酸钙, TOA 对 HNO_3 具有更高的选择性, 特别是在 HNO_3 较低浓度范围内。TOA 可以作为一种有效的溶剂从硝酸和硝酸钙的混合物中提取硝酸, 也是硝酸法生产湿磷酸中提取硝酸的优良萃取剂。

2.1.2 新型萃取剂

除了一些传统萃取剂, 各大研究机构也在着重研发一些新型萃取剂。传统的酸性磷酸酯萃取剂 P204 (二(2-乙基己基)磷酸酯) 和 P507 的萃取性能随着水相酸度的增大而急剧下降, 同时也会产生大量的盐污染废水。为解决这一问题, Han 等^[19] 基于苯环的共轭效应合成了一种耐酸磷酸苯酯萃取剂, DAP (磷酸二酯) 和 MAP (磷酸单酯)。DAP/MAP 对 Ni^{2+} 、 Co^{2+} 和 Mn^{2+} 的萃取率分别为 57.58%、69.42% 和 75.70%, 远大于在相同条件下, P204 和 P507 对 Ni^{2+} 、 Co^{2+} 和 Mn^{2+} 的萃取率。Han 等^[20] 提出了一种新型萃取剂 2-(双((2-乙基己基)氧)磷基)-2-羟基乙酸 (HPOAc), 可从氟吸附型稀土矿硫酸盐浸出液中选择性提取和高效富集稀土元素。结果表明它对金属离子杂质的分离性能优于 P204、P507, 特别是对典型杂质 Al(III) 。Wang 等^[21] 则研制了一种 P-15 萃取剂, 能有效去除湿法磷酸中的镁离子。

结合萃取金属的新材料, Silva 等^[22] 用二-(2-乙基己基)磷酸修饰尼龙-6 纳米纤维, 用于选择性提取锌和镍离子。结果证实这种纳米纤维与传统液-液萃取的效率相等, 但大大减少了有害物质的使用。Yamada 等^[23] 合成了基于硫代磷酸盐和基于磷酸盐的萃取剂 1, 3-二(二氧基硫代磷酰氧基)苯 (Ext 1) 和 1, 3-二(二氧基硫代磷酰氧基)苯 (Ext 2), 并研究了它们从 HCl 和 HNO_3 体系中萃取 Pd^{2+} 能力。Ext 1 择性地提取了 HCl 溶液中 90-99.9% 的 Pd^{2+} 和 HNO_3 单金属溶液中 99.8% 的 Pd^{2+} , 而 Ext 2 在两种溶液中都无法对 Pd^{2+} 进行提取。

对于以上几种常见的萃取剂的优缺点进行总结, 结果如表 3 所示。

表 3 各种萃取剂的优缺点

Table 3 Advantages and disadvantages of various extractants

Extractant	Advantage	Disadvantage	Paper
TBP	Insoluble in water, little impurity content	High price, high density viscosity and difficult to layer	[24]
NOA	Efficient, cheap, easy to use, separate quickly	Poor purification effect of anions, large solubility, high recovery costs, and the purification of high-concentration phosphoric acid is not thorough enough.	[10]
P204, P507	Low price, high extraction rate	Poor selectivity, difficult to reflux, easy to emulsify	[25, 26]
MIBK	Good selectivity, stable operation	Water-soluble, volatile and costly	[27]
N235 (trioctyl tertiary amine)	High extraction rate, mature technology, good selectivity	Volatile, flammable and explosive, susceptible to impurity ions	[28, 29]

2.1.3 复合萃取剂

由于粗磷酸中杂质含量高, 组成复杂, 往往无法通过一种萃取剂完成粗磷酸的纯化, 使用复合萃取剂可以克服单一萃取剂的不足, 提高萃取效率和产品质量, 因此工业上常采用复合净化法达成净化标准。Hu 等^[30] 报道了混合 Cyanex272 和 Cyanex923 萃取剂在硫酸溶液中协同萃取 Sc(III) 的过程。探究了 Sc(III) 在 HCl 、 H_2SO_4 和 $\text{H}_2\text{C}_2\text{O}_4$ 协同体系中的溶出性能。得出结论, 三者的溶出性能表现为: $\text{H}_2\text{C}_2\text{O}_4 > \text{H}_2\text{SO}_4 > \text{HCl}$ 。在低 H_2SO_4 浓度下, Cyanex272 和 Cyanex923 对 Sc(III) 有明显的协同萃取作用。

Jian 等^[31]分别用磺化煤油稀释 N, N-二(1-甲基庚基)乙酰胺(N503)、甲基膦酸二甲庚酯(P350)和 TBP, 从盐酸溶液中萃取铟。发现铟的萃取效率依次为 N503>P350>TBP。铟与 N503 和 P350 萃取剂的配合物为 $[\text{InCl}_4]^-[\text{2S}\cdot\text{H}]^+$; 与 TBP 形成的配合物为 $[\text{InCl}_4]^-[\text{3S}\cdot\text{H}]^+$, 其中 S 为中性萃取剂种类。从含有高浓度盐酸的溶液中提取铟, N503 是三者中最好的萃取剂。Zeng 等^[32]提出用 TBP 和 P507 的混合物为萃取剂, 分离低品位白钨矿盐酸预浸液中的 Mo、W 和 Fe, 研究了不同萃取剂对 TBP 的萃取作用, 发现 P507 对 Mo 和 W 的萃取有协同作用, 对 Fe 的萃取有较强的拮抗作用。Reuna^[33]采用在煤油中稀释过的二-2-乙基己基磷酸(DEHPA)作萃取剂, 从稀磷酸中提取铝。在 pH = 2.5、DEHPA 为 0.6 M、A/O = 1:2 的条件下, 铝的萃取率可达 99%。

我国磷矿品位低, 所制得的湿法磷酸杂质含量高, 磷酸含量低。为了提高从低浓度混合物中萃取磷酸效率, Chen 等^[34]提出了一种由三辛癸烷基叔胺(N235)、异戊醇和磺化煤油组成的混合溶剂, 该溶剂具有萃取量大、溶剂损失小的优点。在低磷酸浓度下, 该混合溶剂的萃取量明显高于大多数常用溶剂, 在分离氯离子和磷酸盐离子方面具有明显的优势, 有利于后续磷肥的生产。

Banerjee 等^[35]建立了乳状液膜萃取废水中六价铬的动力学模型。该团队采用含 O₂ 基部分的单油酸山梨醇、D2EHPA 和煤油分别作为非离子表面活性剂、载体和稀释剂制备该膜。通过考察进料中 HCl 浓度、膜中载体浓度、溶出相 pH 值, 计算出萃取相和溶出相的速率常数。结果表明, 由于萃取速率和溶出速率的差异, 络合扩散速率影响了膜相中 Cr(VI) 的转移和积累。Ncib 等^[36]开发了一种新型聚合物包合膜(PIM), 用于分离铜(II)和镍(II)离子。PIM 由 45%的三乙酸纤维素、40%的 D2EHPA 和 15%的乙酰化硫酸盐木质素组成。通过制备的 PIM, 8 h 后溶液中 Cu(II)的回收率最高可达 88%, Ni(II)的回收率仅为 23%, 优化后的 PIM 从合成废液中提取金属离子的顺序为 $\text{Cu}^{2+}>\text{Cr}^{3+}>\text{Ni}^{2+}$ 。

表 4 中展示了溶剂萃取法去除磷酸中杂质离子的对比。

表 4 溶剂萃取法去除磷酸中杂质离子的对比

Table 4 Comparison of Solvent Extraction Method for Removing Impurity Ions in Phosphoric Acid

Extracted elements	Extractant	O/A ratio	Extraction efficiency	Paper
Fe	12.5%TBP + 87.5%Kerosene	1:1	100%	[37]
	50%P204 + 50%Monoalkyl phosphate	2:1	91%	[38]
	15%TBP + 5%D2EHPA + 80%Kerosene	1:1	99%	[39]
	10%P507 + 20%N235 + 70%Sulfonated kerosene	1:1	89.4%	[40]
H ₃ PO ₄	70%TBP + 30%Isopropyl ether	4:1	76.9%	[41]
	80%TBP + 20%Kerosene	2:1	83%	[42]
	80%TBP + 20%Sulfonated kerosene	6:1	70%	[43]
I	Kerosene	1:2	99.25%	[44]
	Simethicone	3:1	99%	[45]
U	N-propylpropan-1-amine + Kerosene	1:1	95.3%	[46]
	30%TBP + 70%Kerosene	1.5:1	96.67%	[47]
Zn	30%TOA + 20%Iso-octanol + 50%Sulfonated kerosene	2:1	83.75%	[48]
	15%TBP + 5%D2EHPA + 80%Kerosene	1:1	80%	[39]
In	33.33%Ionic liquids + 16.67%P204 + 50%TBP	1:3	98.11%	[49]
	30%D2EHPA + 70%Kerosene	1:5	98.5%	[50]
Sc	P204	1:3	95%	[51]
	10%P204 + 5%TBP + 85%Sulfonated kerosene	1:10	99%	[52]
F	70%TBP + 30%Silicon oil	1:5	98.4%	[53]
Cl	30%N235 + 20%Isooctanol + 50%Sulfonated kerosene	2:1	78.9%	[54]
P ₂ O ₅	90% N-butanol + 10%Isopropyl ether	5:1	90%	[55]
Li	40%TBP + 20%Ethyl butyrate + 40%Kerosene	2:1	87.12%	[56]
Co	30%N235 + 70%Kerosene	2:1	99.997%	[57]
Mg	20%TBP + 80%NOA	1:1	72.11%	[58]
Cu	30%MIBK + 70%TBP	1:1	99%	[59]

2.2 双水相萃取

双水相萃取 (Aqueous two-phase extraction, ATPE) 是一种液-液分离技术, 双水相体系 (ATPS) 指高聚物之间、高聚物与无机盐、正负离子表面活性剂等在水中溶解后形成的互不相溶的两相体系^[60]。聚乙二醇是 ATPE 中使用最广泛的聚合物组分之一, 因为它们价格低廉, 储量丰富, 无毒, 可生物降解且对环境安全^[61]。Guadalupe^[62]等利用聚乙二醇/ Na_2SO_4 水两相体系, 从水溶液中提取磷酸到富聚合物相。磷酸 ATPS 萃取示意图如图 2。实验结果表明大约 75% 的负载 H_3PO_4 有可能转移到富聚合物相, 首次证明了 ATPS 在绿色磷酸净化过程中的可能应用。

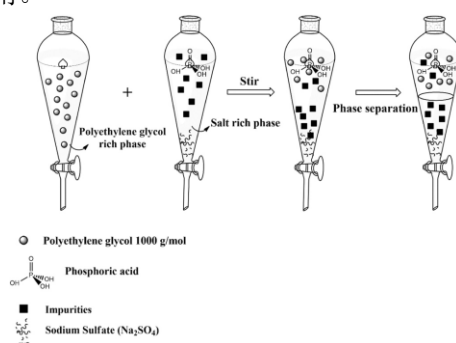


图 2 磷酸 ATPS 萃取示意图^[62]

Fig.2 Phosphoric acid extraction diagram using ATPS^[62]

为了阐明物种转移到水两相体系的富聚合物相的分子机制, Guadalupe 等^[63]采用 ATPS 系统对 H_3PO_4 进行萃取, 利用拉曼光谱法和分子动力学模拟阐明聚乙二醇和磷酸在水两相体系中萃取磷酸的关键相互作用, 提出了一个由氢键相互作用控制的溶剂化机制: 在富含聚合物的水溶液中, 当 H_3PO_4 浓度较低时, 磷酸分子与聚乙二醇的相互作用较弱; 当磷酸浓度增加到一定临界值以上时, 聚乙二醇分子通过氢键与 H_3PO_4 分子发生强烈的相互作用。Sun^[64]等则证明了 ATPS 中 $\text{Cr}(\text{VI})$ 离子进入富含聚乙二醇的相的驱动力为疏水作用, 拓宽了 ATPS 中离子分配性质的解释。

2.3 反胶团萃取

反胶团萃取 (Reverse micelles extraction), 又称为反胶束萃取, 最早用于生物产品的萃取, 近些年来, 也被活跃用于溶液中金属的萃取^[65]。在水溶液的胶束中, 表面活性剂的排列方向是极性基团在外侧与水接触, 非极性基团向内形成一个非极性核, 此时胶束被称为正胶束; 而在有机溶剂中, 表面活性剂的极性基团朝胶束内形成一个极性核, 此时胶束被称为反胶束。亲水物质进入吸水极性核, 达到分离目的。Bley 等^[66]引入了一种预测模型, 该模型用于描述溶剂萃取中反胶束增溶水的现象, 能够更准确地了解和控制溶剂萃取中液相之间的反胶束效应, 为提高核废料管理和湿法冶金回收效率提供了有力的工具。

二壬基萘磺酸 (DNNSA 或 HD) 常被用于反胶团萃取湿法磷酸中的金属离子, 如铁离子^[67]、镁离子等。其中, 在 DNNSA 萃取湿法磷酸溶液中 Mg^{2+} 的过程中, Mg^{2+} 可与反胶团发生化学反应, 形成萃合物 $\text{MD}_2 \cdot 6\text{HD}$, 加快萃取进程^[68]。Luo 等^[69]探究了负载有机相中的反胶束的形态和物理化学特性对相分离行为的影响, 结果表明: 影响相分离行为的最有效的参数是负载有机相的粘度和过量吸水率。Dong 等^[70]报道了季磷型离子液体萃取剂 $[\text{P}_{6,6,6,14}][\text{EHEHP}]$ 和 $[\text{P}_{6,6,6,14}][\text{BTMPP}]$ 在甲苯中协同萃取稀土的首次研究, 揭示了反胶束在稀土元素分离和回收中的优势。 $[\text{P}_{6,6,6,14}][\text{EHEHP}]$ 和 $[\text{P}_{6,6,6,14}][\text{BTMPP}]$ 形成的反向胶束示意图如图 3。

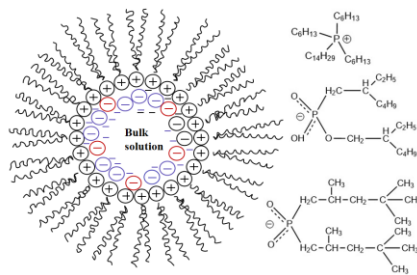


图3 [P_{6,6,6,14}][EHEHP]和[P_{6,6,6,14}][BTMPP]形成的反向胶束示意图^[70]

Fig.3 The schematic reverse micelle formed by [P_{6,6,6,14}][EHEHP] and [P_{6,6,6,14}][BTMPP]^[70]

2.4 超声协助萃取

超声协助萃取 (Ultrasonic assisted extraction, UAE) 是利用超声波其特有的辐射效应作为辅助效果, 从而加速被萃取物质进入萃取溶剂里的一种成熟新型萃取方法。在工业生产磷酸过程中, 往常规净化萃取手段存在速率慢、时间长、萃取用量大、仪器设备复杂等问题。然而, UAE 技术由于其独特的超声空化效应、热效应以及机械效应, 使其具有效率高、速度快、稳定萃取成分化学结构等优点^[71]。图 4 展示了超声空化过程。

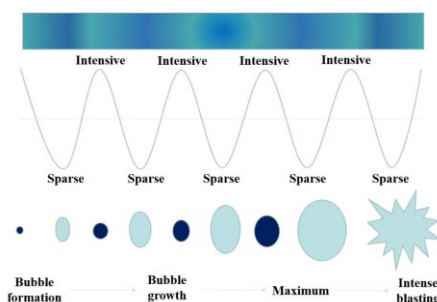


图4 超声空化过程示意图^[72]

Fig.4 Schematic diagram of ultrasonic cavitation process^[72]

Preethi 等^[73]对比了常规分散液-液微萃取, 温控分散液-液微萃取和超声辅助分散液-液微萃取方法在萃取过程中萃取条件对萃取回收率的影响。在这三种方法中, 超声波辅助分散液-液微萃取方法获得了最大的萃取回收率。Zhang 等^[74]在萃取酸洗废水中的锌时, 预处理阶段使用超声强化还原 Fe^{3+} , 大大缩短了处理时间。Xia 等^[75]合成了新型萃取剂 PN-1 萃取湿法磷酸中的 Mg, 建立了超声辅助微通道萃取系统, 发现超声功率为 74 W、O/A 比为 4、水相流速为 $0.2 \text{ mL} \cdot \text{min}^{-1}$ 时, Mg^{2+} 的提取率可达 89.09%。

2.5 超临界流体萃取

研究发现, 当温度和压力超过临界点时, 物质不再具有明确的液态或气态, 而是处于一种介于液、气态之间的超临界状态。而超临界流体萃取 (Supercritical fluid extraction, SFE) 正是利用了物质在超临界条件下的特殊性质的一种分离和提取化合物的新型萃取技术。在这个过程中, 通常使用二氧化碳作为超临界流体实现萃取分离。超临界流体萃取流程图如图 5。

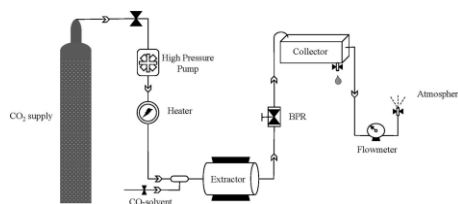


图5 超临界流体萃取之流程图^[76]

Fig.5 A flow diagram of the supercritical fluid extraction^[76]

如今, SFE 已被创新性地运用于湿法磷酸的净化技术中, 其高选择性、条件温和、绿色环保、效率高等优点引起了广泛的关注。采用含有 TBP、D2EHPA 及其加合物的二氧化碳与 HNO_3 进行超临界流体萃取, 从单氮石精矿和磷石膏中萃取稀土金属、钍和铀, SFE 方法可显著提高萃取的效率, 增大被萃取物的成分含量^[77]。影响 SFE 效率的关键因素是螯合剂及相应金属螯合剂的溶解度, Ding 等^[78]通过典型实例说明了主要使用的螯合剂的萃取机理, 详细介绍了原位螯合和在线螯合两种主要的络合方法。尽管 SFE 作为一种新型的绿色萃取技术, 已被广泛应用于多种金属的萃取, 但 SFE 特殊的高压条件带来的成本高、操作要求高、环境要求高的缺点也十分明显, 这也是今后需要研究解决的关键问题之一^[79]。

表 5 对以上五种磷酸的萃取方法进行了对比。

表 5 磷酸主要萃取方法对比

Table 5 Comparison of the main extraction methods of phosphoric acid

Method	Advantage	Disadvantage	Paper
Solvent extraction	Simple process flow, good selectivity, continuous operation, large production capacity, and high separation efficiency	Large amounts of organic solvents	[80]
ATPE	Environmentally friendly, excellent separation efficiency, high product yield, short phase splitting time	The reverse extraction is difficult, the separation of the target compounds is difficult, and the extraction process is unstable	[60, 81, 82]
Reverse micelle extraction	Selective separation and extraction, stable extraction system, mild conditions, flexibility and controllability, energy saving, efficient extraction, and the molecular structure of the compound can be retained during the extraction process	Poor phase separation	[69, 83, 84]
UAE	High efficiency, fast speed, stable extraction of chemical structure	High energy consumption, large-scale equipment, high cost, and the thermal effect is relatively weak	[78, 85]
SFE	Can replace organic solvents and reduce the risk of reaction, moderate critical point, inert, non-toxic, non-flammable, low price, easy to recycle, combined with the high diffusion of gas and good solubility of liquid, almost no secondary waste, and the product is easy to recover	High equipment cost, complex operation, and poor sample versatility	[71, 72, 86]

3 国内外应用情况

湿法磷酸净化技术长久以来就是磷酸制备工艺的一大技术难点, 国外早在 1914 年就开始探索净化湿法磷酸, 并在 20 世纪七八十年代迅速发展出成套食品级磷酸净化技术, 基本可以应付各类磷矿的复杂工况^[87], 但这些技术一直对外保密。目前, 国际上投入工业性生产的主要湿法磷酸净化流程主要有: 巴登化学法、A&W 法、IMI 法、Rhone-Poulenc 法和比利时 Prayon 法等^[88]。其中规模最大、产品质量最稳定的有: 巴登化学法、A&W 法和 Rhone-Poulenc 法。而国内溶剂萃取湿法磷酸技术研究起步较晚, 但经过四十年的发展, 我国溶剂萃取净化湿法磷酸技术已成功研制并打破了国外技术垄断^[89]。溶剂萃取法的国内外应用情况如表 6。目前国内有多家企业和机构在开展湿法磷酸纯化研究, 但在实际生产中取得应用的主要有瓮福集团技术、四川大学技术和华中师范大学技术。其中, 瓮福集团在 2006 年引进以色列 IMI 技术, 并在此基础上进行自主研发, 2010 年开始湿法磷酸净化的工业化, 并与多家化工企业达成合作。四川大学技术和华中师范大学技术则为国产化技术, 工艺不完备, 任有需要完善的地方。截止 2018 年, 国内净化湿法磷酸产能已接近 100 万 t/a。

表 6 溶剂萃取法国内外应用情况^[88, 90-93]

Table 6 Application of solvent extraction method at home and abroad

Technology	Extractant	Final product	Grade	Remark
Weng fu	MIBK	85% Industrial phosphoric acid	Food grade	The domestic scale is about 450,000 t·a ⁻¹
Sichuan University	Mixed solvents (TBP, N-butanol, Isoamyl alcohol, etc.)	75% Phosphoric acid	Industrial grade	The domestic scale is about 210,000 t·a ⁻¹
Central China Normal University	Central China Normal University's patented	85% Industrial phosphoric acid	Industrial grade	The domestic scale is about 60,000 t·a ⁻¹

synergistic extractant				
A&W	MIBK	75%-85%Phosphoric acid	Food grade	The sulfate content of the product is high
Rhone-Poulenc	TBP	60%Food grade phosphoric acid	Food grade	/
IMI	85% Isopropyl ether + 15% N-butanol (or Isopropyl ether)	/	Feed grade	The sulfate content of the product is high
Prayon	Isopropyl ether + TBP	/	Industrial grade or Food grade	The fluorine content of the product is higher
Iprochim/Icechim	N-butanol	/	Industrial grade	The sulfate content of the product is high
Budenheim	Isopropyl ether	75%Industrial phosphoric acid	Industrial grade	Follow by H-type cation exchange resin after extraction

4 磷酸的溶剂萃取法的前景展望

磷酸一直都是我国重要的化工原料。生产磷酸的方法大致分为湿法和热法，但鉴于热法磷酸所需能耗大，对环境污染大，且我国磷矿多为中低品位磷矿，湿法磷酸将成为生产磷酸的大趋势。因湿法磷酸产品杂质含量高，所以开发磷酸纯化技术迫在眉睫。在众多纯化技术中萃取法以其操作简单、绿色环保、成本低廉等优点脱颖而出。但我国湿法磷酸净化技术研究相较于国外起步较晚，近四十年来，我国一直在探索净化湿法磷酸的工艺，国内高校和磷化工公司经过多年相关研究，已经初步掌握了湿法磷酸的净化方法。

本文介绍了湿法磷酸萃取纯化技术，并综述溶剂萃取法、双水相萃取法、反胶团萃取法、超声波萃取法、超临界萃取法的优缺点及其应用，并对不同萃取剂进行了比较。未来磷酸的净化呈现出多种净化技术并存的态势，为此，本文对湿法磷酸净化技术未来的发展方向提出了如下的前景展望：

(1) 溶剂萃取法的研究主要集中在萃取剂上，当前单一萃取剂主要有 TBP 和 MIBK 等，主要探究萃取过程中温度、相比、搅拌时间、离子分配比等的最佳条件。但单一萃取剂往往无法满足多种离子的萃取纯化，未来溶剂萃取将主要集中在复合萃取剂的研发上。复合萃取剂结合多种萃取剂，可通过实验探究最佳分配比，大大提高萃取效率。同时，多种技术耦合高效集成实现磷酸的净化是大势所趋。开发新型萃取剂，研究新型萃取方法，使萃取剂和各种材料结合，实现湿法磷酸萃取的绿色化和高效化需求。

(2) 双水相萃取和反胶团萃取最大的特点就是绿色环保，操作简单。二者最初都应用于生物提取上，但近些年关于离子萃取上的研究也逐渐增多，这些主要集中于处理重金属离子等有害物质。双水相萃取的研究主要集中在探索新的双水相体系。二者在离子提纯方面仍然处于探索阶段，其应用范围和效果还有待进一步验证和完善。

(3) 超声协助萃取重点在“协助”，利用超声波技术辅助，可加快萃取进程，具有极大的应用前景。超临界流体萃取萃取效率高，对环境污染小，但一方面，超临界流体对大部分离子的溶解度较低，需要进一步研究如何提高离子的溶解度和萃取效率。另一方面，超临界流体萃取技术的成本较高，需要进一步降低成本才能在实际中得到更广泛的应用。预测超临界流体萃取技术将来会和其他技术结合，应用于特定领域。

参 考 文 献

- [1] HUANG M-Y, YANG S-K, LI J, et al. Study on technology for purification of WPA by solvent extraction process [J]. Phosphate & Compound Fertilizer, 2004, 19(4): 9.
黄美英, 杨三可, 李军, 等. 溶剂萃取法净化湿法磷酸的工艺研究 [J]. 磷肥与复肥, 2004, 19(4): 9.
- [2] ZHONG B-H, LI J, GUO X-D, et al. Current research status and development direction of purification technology of wet-process phosphoric acid [J]. Inorganic Chemicals Industry, 2008, (02): 9.
钟本和, 李军, 郭孝东, 等. 湿法磷酸净化技术研究现状及发展方向 [J]. 无机盐工业, 2008, (02): 9.

- [3] YU L-Y, LIU S-B, JIA S-Z, et al. Current Status and Research Progress of Purification Technology of Electronic Grade Phosphoric Acid [J]. *CIESC Journal*, 2024, 75(01): 1.
余留洋, 刘书博, 贾晟哲, 等. 电子级磷酸的纯化精制技术发展现状与研究进展 [J]. *化工学报*, 2024, 75(01): 1.
- [4] RYSZKO U, RUSEK P, KOŁODYŃSKA D. Quality of Phosphate Rocks from Various Deposits Used in Wet Phosphoric Acid and P-Fertilizer Production [J]. *Materials*, 2023, 16(2): 793.
- [5] YANG J-Z, LI Z-X. Technology for purification of wet process phosphoric acid [J]. *Phosphate & Compound Fertilizer*, 2004, (06): 13.
杨建中, 李志祥. 湿法磷酸的净化技术 [J]. *磷肥与复肥*, 2004, (06): 13.
- [6] GONG X, HU C, JIN Y, et al. Preparation of refined phosphoric acid with recycling of raffinate acid by the extraction of metal impurities [J]. *Journal of Cleaner Production*, 2024, 434: 140158.
- [7] FLETT D S. Principles and practices of solvent extraction. Second Edition, Revised and Expanded. Edited by J Rydberg, M Cox, C Musikas and GR Choppin. Marcel Dekker, New York, 2004. 760 pp, ISBN 0 8247 5053 2 [J]. *Journal of Chemical Technology & Biotechnology*, 2005, 80(3): 359.
- [8] KENZA B, MEHDI M M E, HANANE B, et al. Recent progress in heavy metals extraction from phosphoric acid: A short review [J]. *J Ind Eng Chem*, 2022, 115: 120.
- [9] YANG J-P. Technology of Purification of Wet-Process Phosphoric Acid by Solvent Extraction [D]. Beijing: China University of Petroleum, 2020.
杨佳朋. 溶剂萃取法净化湿法磷酸技术开发 [D]. 北京: 中国石油大学, 2020.
- [10] AMIN M I, ALI M M, KAMAL H M, et al. Recovery of high grade phosphoric acid from wet process acid by solvent extraction with aliphatic alcohols [J]. *Hydrometallurgy*, 2010, 105(1-2): 115.
- [11] MAGDA A A, ABDUL FATAH M Y, MOHSEN M A, et al. Liquid-liquid extraction technique for purification of Egyptian WET process phosphoric acid [J]. *Periodica Polytechnica Chemical Engineering*, 2010, 54(2): 57.
- [12] ZHU G, YANG Y, HE L, et al. Novel Synergistic Process of Impurities Extraction and Phosphogypsum Crystallization Control in Wet-Process Phosphoric Acid [J]. *ACS Omega*, 2023, 8(31): 28122.
- [13] MARTINEZ D M, ACHER E, VATIN M, et al. Aggregation of Bifunctional Extractants Used for Uranium(VI) Separation [J]. *Journal of Physical Chemistry B*, 2021, 125(38): 10759.
- [14] WANG L, WANG Y, CUI L, et al. A sustainable approach for advanced removal of iron from CFA sulfuric acid leach liquor by solvent extraction with P507 [J]. *Separation and Purification Technology*, 2020, 251: 117371.
- [15] TORABI S A, GHANADZADEH GILANI H, AZADIAN M, et al. Ternary Liquid-Liquid Equilibrium for Phosphoric Acid Extraction from Aqueous Solutions with 1-Pentanol or Methyl Butyl Ketone at T = (298.2, 308.2, and 318.2) K [J]. *Journal of Chemical & Engineering Data*, 2021, 66(6): 2401.
- [16] CHEN M, LI J, JIN Y, et al. Efficient solvent extraction of phosphoric acid with dibutyl sulfoxide [J]. *Journal of Chemical Technology & Biotechnology*, 2017, 93(2): 467.
- [17] CAO Y, HU X, WU J, et al. Liquid-Liquid Equilibrium in the Nitric Acid + Calcium Nitrate + Water + Tri-n-octylamine System [J]. *Journal of Chemical & Engineering Data*, 2021, 66(2): 890.
- [18] CAO Y, HU X, DONG Y, et al. Liquid-Liquid Equilibria of the System Nitric Acid + Phosphoric Acid + Calcium Nitrate + Water + Tri-n-Octylamine at 298.15 K [J]. *Journal of Chemical & Engineering Data*, 2023, 68(5): 1154.
- [19] HAN B, LI S, CHANG D, et al. Efficient phenyl phosphate ester extractant synthesis and solvent extraction performance evaluation for transition metals [J]. *Separation and Purification Technology*, 2024, 336.

- [20] HAN J, LI Y, LI S, et al. Efficient enrichment and selective recovery of rare earths from sulfate leachate of ion-adsorption type rare earth ore by extraction with HPOAc [J]. *Journal of Rare Earths*, 2023.
- [21] WANG B, ZHOU Q, CHEN C, et al. Separation of phosphoric acid and magnesium from wet process phosphoric acid by solvent extraction [J]. *Canadian Metallurgical Quarterly*, 2022, 62(4): 791.
- [22] NUNES DA SILVA F, BASSACO M M, BERTUOL D A, et al. An eco-friendly approach for metals extraction using polymeric nanofibers modified with di-(2-ethylhexyl) phosphoric acid (DEHPA) [J]. *Journal of Cleaner Production*, 2019, 210: 786.
- [23] YAMADA M, RAJIV GANDHI M, KUNDA U M R, et al. Recovery of Pd(II) from leach solutions of automotive catalysts by solvent extraction with new thiophosphate extractants [J]. *Hydrometallurgy*, 2020, 191: 105221.
- [24] QI Y-B, ZHANG S-J. New research progress and present application situation of purification technology for wet-process phosphoric acid [J]. *Applied Chemical Industry*, 2022, 51(09): 2798.
齐亚兵, 张思敬. 湿法磷酸净化技术研究新进展及应用现状 [J]. *应用化工*, 2022, 51(09): 2798.
- [25] YANG T, SUN G-X, QIAN Y, et al. Separation of hafnium from zirconium in hydrochloric acid solution with di(2-ethylhexyl)phosphoric acid by solvent extraction [J]. *Nuclear Science and Techniques*, 2019, 30(02): 53.
- [26] SUN S, SUN Q-H, SONG J, et al. Current status of scandium resources and application research progress of solvent extraction in the process of scandium extraction [J]. *The Chinese Journal of Process Engineering*, 2020, 20(08): 877.
孙帅, 孙宏骞, 宋静, 等. 钪资源现状及溶剂萃取在钪提取过程中的应用研究进展 [J]. *过程工程学报*, 2020, 20(08): 877.
- [27] LIU J-D, WANG J-J, WEI-LI, et al. Research Progress of Tantalum Extraction [J]. *Conservation and Utilization of Mineral Resources*, 2021, 41(02): 163.
刘建迪, 王静静, 李伟, 等. 钽的提取研究进展 [J]. *矿产保护与利用*, 2021, 41(02): 163.
- [28] SONG Q, TONG X, XIE X, et al. Research status and prospect of separation and extraction of nickel and cobalt by solvent extraction [J]. *The Chinese Journal of Nonferrous Metals*, 2023, 33(06): 1957.
宋强, 童雄, 谢贤, 等. 溶剂萃取法分离提取镍和钴的研究现状及展望 [J]. *中国有色金属学报*, 2023, 33(06): 1957.
- [29] XIANG X-Y, YE G-H, ZHU S-Q, et al. Solvent Extraction of Vanadium from Vanadium-bearing Acid Leaching Solution [J]. *Conservation and Utilization of Mineral Resources*, 2023, 43(05): 170.
项新月, 叶国华, 朱思琴, 等. 从含钒酸浸液中萃取提钒的研究进展 [J]. *矿产保护与利用*, 2023, 43(05): 170.
- [30] HU J, ZOU D, CHEN J, et al. A novel synergistic extraction system for the recovery of scandium (III) by Cyanex272 and Cyanex923 in sulfuric acid medium [J]. *Separation and Purification Technology*, 2020, 233: 115977.
- [31] JIAN D, GUO X, LI X, et al. Extraction of indium with N,N-di(1-methylheptyl)acetamide, di(1-methylheptyl)methyl phosphate, and tributylphosphate by solvent extraction in hydrochloric acid solution [J]. *Minerals Engineering*, 2020, 156.
- [32] ZENG L, YANG T, YI X, et al. Separation of molybdenum and tungsten from iron in hydrochloric-phosphoric acid solutions using solvent extraction with TBP and P507 [J]. *Hydrometallurgy*, 2020, 198: 105500.
- [33] REUNA, SINI, Väisänen, et al. Purification of recovered phosphoric acid by extracting aluminium with di-2-ethylhexyl phosphoric acid [J]. *Chemical Papers*, 2021, 76(prepublish): 332.
- [34] CHEN H, SUN Z, SONG X, et al. Efficient Extraction of Phosphoric Acid with a Trialkyl Amine-Based

- Solvent Mixture [J]. *J Chem Eng Data*, 2015, 61(1): 438.
- [35] BANERJEE S, SIVAMANI S. Estimation of Model Parameters in the Extraction of Cr(VI) from Wastewater by an Emulsion Liquid Membrane [J]. *Chemical Engineering & Technology*, 2022, 45(6): 1141.
- [36] SANA N, AMEL C, AFEF B, et al. Separation of copper and nickel from synthetic wastewater by polymer inclusion membrane containing di(2-ethylhexyl)phosphoric acid [J]. *Polymer Bulletin*, 2022, 80(11): 12177.
- [37] ZHIJIN H, TAO Z, LI L, et al. Extraction performance and mechanism of TBP in the separation of Fe^{3+} from wet-processing phosphoric acid [J]. *Separation and Purification Technology*, 2021, 272.
- [38] ZHANG W-K, GONG Y-L, GAO K-G. Study on the synergistic extraction of iron ions in WPA by P204 and P538 [J]. *Phosphate & Compound Fertilizer*, 2021, 36(04): 4.
张文凯, 龚元琳, 高凯歌. 二-(2-乙基己基)磷酸酯与单烷基磷酸酯协同萃取湿法磷酸中铁离子的研究 [J]. *磷肥与复肥*, 2021, 36(04): 4.
- [39] AZIZITORGHABEH A, RASHCHI F, BABAKHANI A. Stoichiometry and structural studies of Fe(III) and Zn(II) solvent extraction using D2EHPA/TBP [J]. *Separation and Purification Technology*, 2016, 171: 197.
- [40] ZHU X, LIU Y, MA C, et al. Effective separation of V(IV) and Fe(III) from sulfuric acid solution by solvent extraction with P507 and N235 [J]. *Hydrometallurgy*, 2024, 224: 106228.
- [41] ZAIKUN W, LIUXING S, PENG Y, et al. Extraction of H_3PO_4 from low-grade phosphate rocks leachate of HCl-route by the mixture of TBP and IPE: Optimization, mass transfer and mechanism [J]. *Journal of Molecular Liquids*, 2023, 370: 120861.
- [42] ZHANG S, CHEN Y, ZHANG T, et al. Separation of H_3PO_4 from HCl-wet-processing phosphate rocks leach liquor by TBP: Extraction equilibria and mechanism study [J]. *Separation and Purification Technology*, 2020, 249: 117156.
- [43] LIU, HAOZHOU, YANG, et al. A non-aqueous phase extraction system using tributyl phosphate for H_3PO_4 separation from wet-process superphosphoric acid: Extraction equilibrium and mechanism [J]. *Korean Journal of Chemical Engineering*, 2022, 39(7): 1659.
- [44] KAMAL B, RACHID B, KHAOULA K. A novel and complete process for iodine extraction and recovery from industrial wet-process phosphoric acid based on chemical oxidation and solvent extraction [J]. *Process Safety and Environmental Protection*, 2023, 176: 332.
- [45] HE S, CHEN Q, AO X, et al. A method for the removal of trace iodine from wet-process phosphoric acid [J]. *Hydrometallurgy*, 2020, 191.
- [46] ORABI A H, MOHAMED B T, ELYAN S S. Simultaneous separation of rare earths and valuable actinoid element from wet process phosphoric acid using N-propylpropan-1-amine extractant [J]. *Hydrometallurgy*, 2021, 205: 105749.
- [47] GHAEMI A, HEMMATI A. Experimental investigation of uranium extraction from the industrial nuclear waste treatment plant by tri-butyl-phosphate [J]. *Journal of Radioanalytical and Nuclear Chemistry*, 2021, 327(3): 1237.
- [48] XU C, ZHOU J, YIN S, et al. Solvent extraction and separation of zinc-iron from spent pickling solution with tri-n-octylamine [J]. *Separation and Purification Technology*, 2021, 278: 119579.
- [49] GAO L, DAI Z, WU H, et al. Study on efficient extraction of indium from complex sulfuric acid solution by “ionic liquid + di(2-ethylhexyl)phosphoric acid + tributyl phosphate” [J]. *Separation and Purification Technology*, 2022, 288: 120670.
- [50] DENG Z, LI X, WEI C, et al. Recovery of Indium from Hard Zinc Slag by Pressure Leaching and

- Solvent Extraction [J]. *Jom*, 2021, 73(2): 721.
- [51] YE Q, LI G, DENG B, et al. Solvent extraction behavior of metal ions and selective separation Sc^{3+} in phosphoric acid medium using P204 [J]. *Separation and Purification Technology*, 2019, 209: 175.
- [52] ZHOU J, MA S, CHEN Y, et al. Recovery of scandium from red mud by leaching with titanium white waste acid and solvent extraction with P204 [J]. *Hydrometallurgy*, 2021, 204: 105724.
- [53] ZUO Y, CHEN Q, LI C, et al. Removal of Fluorine from Wet-Process Phosphoric Acid Using a Solvent Extraction Technique with Tributyl Phosphate and Silicon Oil [J]. *ACS Omega*, 2019, 4(7): 11593.
- [54] YAO J, LI Y, SRINIVASAKANNAN C, et al. Extraction of chloride from slag flush wastewater using solvent N235 [J]. *Hydrometallurgy*, 2022, 213: 105934.
- [55] WU Z, PENG Y, LI J, et al. The mass transfer and mechanism of H_3PO_4 from low concentration HCl-route wet-process phosphoric acid by the mixture of n-butanol and isopropyl ether [J]. *Separation and Purification Technology*, 2022, 281: 119851.
- [56] SHI C-L, SONG G-X, QING Y-R, et al. Synergistic extraction of lithium with tributyl phosphate / ethyl butyrate system [J]. *Chemical Engineering*, 2020, 48(02): 16.
石成龙, 宋桂秀, 秦亚茹, 等. 磷酸三丁酯/丁酸乙酯体系协同萃取提锂的研究 [J]. *化学工程*, 2020, 48(02): 16.
- [57] JU J, FENG Y, LI H, et al. Separation of Cu, Co, Ni and Mn from acid leaching solution of ocean cobalt-rich crust using precipitation with Na_2S and solvent extraction with N235 [J]. *Korean Journal of Chemical Engineering*, 2022, 39(3): 706.
- [58] YE C, LI J. Wet process phosphoric acid purification by solvent extraction using N-octanol and tributylphosphate mixtures [J]. *Journal of Chemical Technology & Biotechnology*, 2013, 88(9): 1715.
- [59] MEHDI I, AFZALI Z, HAGHIGHI H K. Solvent Extraction of Copper Using TBP, D2EHPA and MIBK [J]. *Russian Journal of Non-Ferrous Metals*, 2018, 59(6): 605.
- [60] QU F, LV F-H, ZHANG H-J. Smart Polymer Based Aqueous Two-Phase Systems Applied in Bio-Molecule Separation and Purification [J]. *Progress in Chemistry*, 2010, 22(01): 125.
屈锋, 吕锋华, 张慧娟. 智能聚合物的双水相体系在生物分子分离纯化中的应用 [J]. *化学进展*, 2010, 22(01): 125.
- [61] VOSHKIN A, SOLOV'EV V, KOSTENKO M, et al. A Doubly Green Separation Process: Merging Aqueous Two-Phase Extraction and Supercritical Fluid Extraction [J]. *Processes*, 2021, 9(4): 727.
- [62] FALCON-MILLAN G, PILAR GONZALEZ-MUÑOZ M, DURAND A, et al. Phosphoric acid partition in aqueous two phase systems [J]. *Journal of Molecular Liquids*, 2017, 241: 967.
- [63] FALCON-MILLAN G, REYES-AGUILERA J A, RAZO-LAZCANO T, et al. Raman Spectroscopy and Molecular Dynamics Simulations of Aqueous Two-Phase Systems for the Purification of Phosphoric Acid [J]. *Physical Chemistry Chemical Physics*, 2023.
- [64] SUN P, HUANG K, LIN J, et al. Role of Hydrophobic Interaction in Driving the Partitioning of Metal Ions in a PEG-Based Aqueous Two-Phase System [J]. *Industrial & Engineering Chemistry Research*, 2018, 57(33): 11390.
- [65] MAO X-H, LIU D-J. Kinetics of Titanium Extraction from Hydrochloric Acid Solution with Reverse Micelles [J]. *Journal of Chemical Engineering of Chinese Universities*, 2018, 32(01): 92.
毛雪华, 刘代俊. 反胶团萃取盐酸溶液中钛的动力学 [J]. *高校化学工程学报*, 2018, 32(01): 92.
- [66] BLEY M, SIBOULET B, KARMAKAR A, et al. A predictive model of reverse micelles solubilizing water for solvent extraction [J]. *J Colloid Interface Sci*, 2016, 479: 106.
- [67] CAO Y, LIU D-J, XU B, et al. Study of Mechanism of Fe^{3+} Extraction from Wet-process Phosphoric Acid by DNNSA Reversed Micelle [J]. *Sulphur Phosphorus & Bulk Materials Handling Related*

- Engineering, 2008, (04): 1.
曹艳, 刘代俊, 徐碧,等. DNNSA 反胶团萃取湿法磷酸中 Fe^{3+} 的机理研究 [J]. 硫磷设计与粉体工程, 2008, (04): 1.
- [68] YU J, LIU D-J, DU H-M, et al. Reverse Micelles Extraction of Magnesium from Phosphoric Acid Solution [J]. Journal of Chemical Engineering of Chinese Universities, 2008, (03): 401.
余静, 刘代俊, 杜怀明,等. 反胶团萃取磷酸溶液中的镁 [J]. 高校化学工程学报, 2008, (03): 401.
- [69] LUO Y, HU H, WANG Y, et al. Phase separation in solvent extraction of copper or nickel from acidic solution using a sulfonic acid (HDNNS) and a carboxylate ester (4PC) [J]. Journal of Dispersion Science and Technology, 2019, 40(6): 819.
- [70] YAMIN DONG X S, YANLIANG WANG, YUJUN CHAI. Reversed Micelle Synergistic Extraction from Phosphonium Ionic Liquid Extractants in Diluent for Rare Earth [J]. behalf of the AIChE, February 18, 2016: 2163
- [71] JIN Y, LI J, ZOU D, et al. Effect of ultrasonic treatment on extraction of phosphoric acid with tri-n-butyl phosphate [J]. Modern Chemical Industry, 2015, 35(09): 77.
金央, 李军, 邹达,等. 超声波对磷酸三丁酯萃取磷酸过程的影响 [J]. 现代化工, 2015, 35(09): 77.
- [72] YAN W-J, PAN D-A, LI B. Application of ultrasonic intensification in hydrometallurgy leaching process [J]. The Chinese Journal of Process Engineering, 2020, 20(11): 1241.
焉杰文, 潘德安, 李彬. 超声强化在湿法浸出过程中的应用 [J]. 过程工程学报, 2020, 20(11): 1241.
- [73] A P, R V, A B L. Dispersive liquid-liquid microextraction of zinc from environmental water samples using ionic liquid [J]. Chemical Engineering Communications, 2021, 208(6): 914.
- [74] ZHANG J, LEI Y, HU S, et al. Ultrasonic pretreatment-solvent extraction process for separating zinc from pickling waste liquid [J]. Journal of Environmental Chemical Engineering, 2023, 11(6): 111160.
- [75] QI X, JIANGPO Z, XIAOFENG H, et al. Ultrasound-Assisted Micro-Channel Extraction of Magnesium from Wet-Process Phosphoric Acid [J]. Solvent Extraction Research and Development, Japan, 2022, 29(1): 9.
- [76] AHANGARI H, KING J W, EHSANI A, et al. Supercritical fluid extraction of seed oils – A short review of current trends [J]. Trends in Food Science & Technology, 2021, 111: 249.
- [77] SAMSONOV M D, TROFIMOV T I, KULYAKO Y M, et al. Supercritical fluid extraction of rare earth elements, thorium and uranium from monazite concentrate and phosphogypsum using carbon dioxide containing tributyl phosphate and di-(2-ethylhexyl)phosphoric acid [J]. Russian Journal of Physical Chemistry B, 2016, 10(7): 1078.
- [78] DING X, LIU Q, HOU X, et al. Supercritical Fluid Extraction of Metal Chelate: A Review [J]. Critical Reviews in Analytical Chemistry, 2016, 47(2): 99.
- [79] HONG G C, CHING T M, PIN Y S, et al. A Review on Extraction Techniques and Its Future Applications in Industry [J]. European Journal of Lipid Science and Technology, 2021, 123(4).
- [80] LI L-Q, YANG L, ZHENG M-H, et al. Research Progress of Extraction Separation Technology and Extractants for Rare Earth [J]. Journal of Rare Earths, 2022, 40(06): 920.
李立清, 杨林, 郑明豪,等. 稀土萃取分离技术及萃取剂研究进展 [J]. 中国稀土学报, 2022, 40(06): 920.
- [81] WENZHUO X, XINPEI G, LIQIANG Z, et al. Ionic-Liquid-Based Aqueous Two-Phase Systems Induced by Intra- and Intermolecular Hydrogen Bonds [J]. Molecules, 2022, 27(16): 5307.
- [82] ANDREY V, VITALIY S E, MIKHAIL K, et al. A Doubly Green Separation Process: Merging Aqueous Two-Phase Extraction and Supercritical Fluid Extraction [J]. Processes, 2021, 9(4): 727.
- [83] BUKMAN L, FERNANDES-MACHADO N R C, CAETANO W, et al. Treatment of wastewater

- contaminated with ionic dyes: Liquid-liquid extraction induced by reversed micelle followed by photodegradation [J]. *Separation and Purification Technology*, 2017, 189: 162.
- [84] NAGANAWA H, SUZUKI H, YANASE N, et al. Reversed-Micellar Extraction of Strontium(II) from Model Solutions of Seawater; Original Papers [J]. *Analytical Sciences*, 2011, 27(3): 321.
- [85] O. K M, B. U K, YU. S M, et al. Supercritical Fluid Extraction of Cerium from Aqueous Solutions Using Tributyl Phosphate as a Ligand [J]. *Russian Journal of Physical Chemistry B*, 2023, 16(8): 1305.
- [86] WANG Y, LI R, JIANG Z-T, et al. Green and solvent-free simultaneous ultrasonic-microwave assisted extraction of essential oil from white and black peppers [J]. *Industrial Crops & Products*, 2018, 114: 164.
- [87] HE H-M. Comprehensive utilization of phosphate rock resources and related new techniques [J]. *Phosphate & Compound Fertilizer*, 2022, 37(08): 34.
何浩明. 磷矿资源综合利用及新型工艺技术探讨 [J]. *磷肥与复肥*, 2022, 37(08): 34.
- [88] GILMOUR R. *Phosphoric Acid: Purification, Uses, Technology, and Economic* [M]. 1st ed. Boca Raton: CRC Press, 2013.
- [89] WANG X-L, XU D-H, ZHONG Y-J, et al. Future trend and development course of phosphorus chemical industry for sixty years in China [J]. *Inorganic Chemicals Industry*, 2020, 52(10): 9.
王辛龙, 许德华, 钟艳君, 等. 中国磷化工行业 60 年发展历程及未来发展趋势 [J]. *无机盐工业*, 2020, 52(10): 9.
- [90] HOU Y-X, CHEN Z-F, WU J, et al. The Application and Advantage of Wet Process Phosphoric Acid Refining Technology of Central China Normal University [J]. *Chemical Fertilizer Design*, 2018, 56(03): 1.
侯炎学, 陈志孚, 吴杰, 等. 华中师范大学湿法磷酸精制技术的应用及优势 [J]. *化肥设计*, 2018, 56(03): 1.
- [91] WANG Z-J, WEI C-T. Progress on research of purification technology for wet-process phosphoric acid [J]. *Industrial Minerals & Processing*, 2019, 48(10): 50.
王智娟, 韦昌桃. 湿法磷酸净化技术研究进展 [J]. *化工矿物与加工*, 2019, 48(10): 50.
- [92] TIAN W-H, ZHANG C-H, CHEN Y-H, et al. Application status of purification technology of WPA by solvent extraction method [J]. *Phosphate & Compound Fertilizer*, 2019, 34(03): 24.
田文航, 张才华, 陈元辉, 等. 溶剂萃取法湿法磷酸净化技术应用现状 [J]. *磷肥与复肥*, 2019, 34(03): 24.
- [93] ZHONG B-H, CHEN L, LI J, et al. Current Status of Purifying Wet-process Phosphoric Acid by Solvent Extraction Method in China [J]. *Sulphur Phosphorus & Bulk Materials Handling Related Engineering*, 2006, (06): 1.
钟本和, 陈亮, 李军, 等. 溶剂萃取法净化湿法磷酸国内近况 [J]. *硫磷设计与粉体工程*, 2006, (06): 1.